


فرآورده های فرعی / بخش کوره بلند

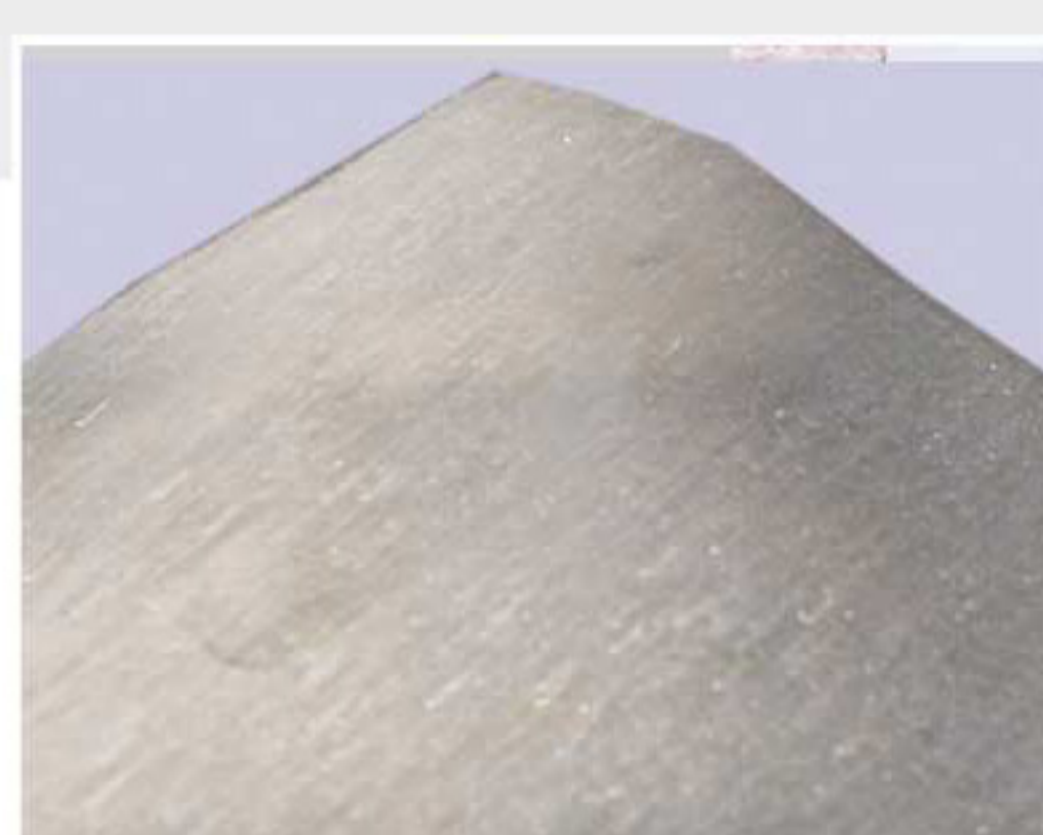

مشخصات سرباره کوره بلند:

34-40%	SiO ₂
34-40%	CaO
10 -12%	Al ₂ O ₃
7-10%	MgO
0.6-2 %	MnO
0.45 - 0.7%	FeO
1.5-2.5%	TiO ₂
0.02-0.06 %	V ₂ O ₅
0.5-0.8 %	Na ₂ O
0.55-1.15%	K ₂ O
1.0-1.55%	S
0.85-1.15%	CaO/SiO ₂
1-7%	H ₂ O

گرد و غبار کوره بلند:

22 - 42%	Tfe
4 - 8 %	CaO
6 - 9%	SiO ₂
0.5 - 1 %	MnO
0.3 - 0.65%	S
3 - 12%	H ₂ O
25 - 45%	L.O.I
20 - 40%	C
8 - 15%	FeO

دانه بندی سرباره

0-3mm	Min90%
-------	--------